

COB-2023-1156
**FINITE ELEMENT ANALYSES MODELING FOR ADDITIVE
MANUFACTURING TRACKING THERMAL AND MECHANICAL
PROPERTIES IN LATTICE STRUCTURES**

Euclides Santanna

Carla Anflor

University of Brasilia (UnB), UnB-Gama campus, Brasilia, DF 72.444-240 Brazil.

euclidesunb@gmail.com

anflor@unb.br

Abstract. Additive manufacturing (AM) has been gaining ground within industries in the last century. Fabrication methods involving metallic dies have been used in several areas of engineering, where lightweight and durable components are required. In the search for shape and performance optimization, we have the study of fill geometries, known as lattice structures. Some of the geometries have negative Poisson's ratio, as in the case of auxetic structures, or optimized mass/volume ratio, as in the Gyroid structure. The objective of this work is to analyze and characterize the metallic additive manufacturing of the Selective Laser Melting (SLM) type, and its influence on complex geometries such as the lattice structures. Through computer simulations using the ANSYS® software, finite element analysis studies will be carried out, characterizing the effects of the manufacturing process in AM.

Keywords: Additive Manufacture, Selective Laser Melting, Tripple periodic minimal surface, Gyroid, Lattice Structures.

1. INTRODUCTION

The search for lighter and stronger materials and geometries has been a goal for several industries, such as aerospace, automotive, and biomedical (Michael Ashby et al., 2019). In this sense, additive manufacturing (AM), popularly known as 3D printing, has gained prominence for its versatility and ability to produce complex geometries.

The AM process consists of manufacturing a geometry layer by layer using a material, with each layer representing a cross-sectional representation of the geometry. In 1979, Ross F. Housholder presented the initial description of a laser sintering AM system using powder. The material was deposited in thin, flat layers and sintered by a laser beam, solidifying the material through heat (Bourell et al., n.d.). The process described by Housholder later became known as Selective Laser Sintering (SLS).

From a derivation of this process, the Selective Laser Melting (SLM) process was created in the mid-1990s by the Fraunhofer Institute for Laser Technology (ILT) in Aachen, Germany, which uses metal alloy powders for the construction of its geometries. One of the main advantages of the SLM process is the ability to use metal alloys, such as titanium, which have high corrosion resistance, high toughness, and creep resistance. Another positive point is the cost reduction compared to conventional material subtraction processes, such as machining.

Despite all the benefits of the AM process using the SLM method, it still lacks the ability to produce large parts, being limited to small parts manufactured in generally inert chambers (Milewski, 2017).

For the composition and construction of the internal geometry of AM parts, it is necessary to use infill, which can be formed by an interconnected network of structural solids, such as plates made up of edges and faces of a cell. Within this class, a structure called cellular solids stands out, which has a wide application in engineering due to its mass/volume ratio known as a gyroid (Khaderi et al., 2014).

In studying its structure, we can observe a similarity with objects and structures found in nature, possessing a high level of interconnectivity and porosity. Due to these characteristics, the structure discovered by Alan Schonon in 1970 is naturally optimized, possessing greater rigidity and dimensional stability. The gyroid is part of the so-called triply periodic minimal surfaces (TPMS), structures that can be found in butterfly wings and beetle shells (Winter et al., 2015).

From a manufacturing point of view, structures belonging to the TPMS group present several challenges due to their high degree of interconnectivity and complexity. However, with the advent of AM, complex structures like the gyroid can be manufactured more easily compared to conventional methodologies. Additionally, AM allows the production of customized and small quantity parts, making it an attractive option to produce bespoke parts and low-volume prototypes.

Simulation study allows for a more in-depth analysis of the structure's properties, such as tensile, compression, bending, and fatigue resistance. This information is crucial for the development of new applications and materials, as well as for the validation of the use of these structures in specific applications.

The use of structures such as the gyroid in aerospace and automotive applications has shown promise, as these structures have a high strength-to-weight ratio. Still, it is essential to consider the challenges associated with the manufacturing of these structures, as well as mechanical properties and durability over time.

In this context, finite element simulation is a valuable tool for the study and analysis of complex structures manufactured by AM, allowing for the identification of possible failures and the development of more efficient solutions. Studies of this nature hold the potential to significantly bolster the progress of AM and its associated technologies, while also fostering widespread adoption of intricate structures across diverse industry sectors. The main goal of this work relies on apply a AM methodology to fabricate complex geometries and investigate the warping effects resulting from the laser-material interaction process. The focus is on understanding the occurrence of failures and defects that may arise during the manufacturing process.

2. STRUCTURE MODELING

The structure employed the principles of the Gauss-Bonnet theorem to construct the triple periodic minimal surface (TPMS) in the parametric creation of the Gyroid geometry (Hyde et al., 1997). The nodal equation (Eq. 1) was incorporated into a Python script to generate the geometry, enabling the customization of multiple dimensional parameters. Within these TPMS structures, two different types of architecture exist. Bicontinuous TPMS are smooth infinite surfaces that partition space into two intertwined labyrinthine domains and exhibit three distinct lattice periodic (Kapfer et al., 2011).

For the construct of the Gyroid geometry (Fig.1) a Python programming routine was developed for the implementation of this structure. The Cartesian variables x , y , and z were employed to represent the coordinates, enabling the definition of the structure's positioning and dimensions. The selected cellular structure had overall dimensions of 40mm x 40mm x 40mm, with a relative fill density of 25% of the total volume of the geometry. The wall thickness of the structure was set at 2mm.

$$F(x, y, z) = \sin(2\pi x/a) \cos(2\pi y/a) + \sin(2\pi y/a) \cos(2\pi z/a) + \sin(2\pi z/a) \cos(2\pi x/a) \quad (1)$$

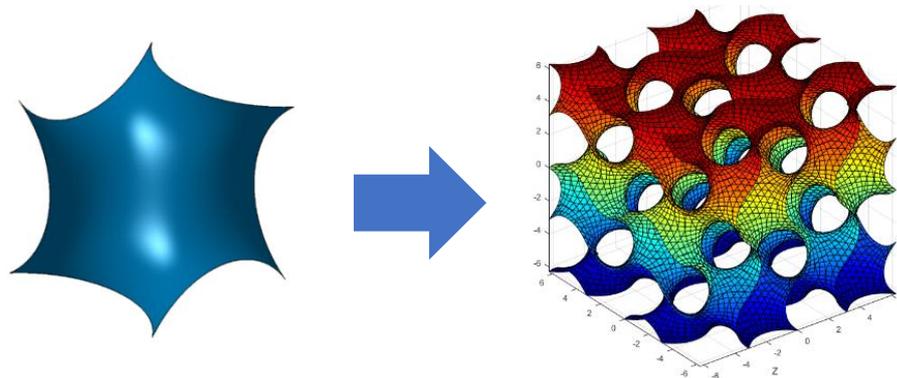


Figure 1. Gyroid lattice Structure.

2.1 Numerical simulation

To model and evaluate simulation data in AM, a thermal-transient analysis was conducted. This involved applying thermal loads generated during the laser-based fabrication process along the cross-section of the geometry (Xiao & Zhang, 2007). The results of this analysis were used as input parameters for a static structural analysis, aimed at assessing the impact of the thermal loading on the structure.

The thermal analysis, in conjunction with the AM module, simulated the layer-by-layer construction of the geometry. Metallic powder material was sintered using a laser beam, similar to SLM (Selective Laser Melting) process. This interaction created a temperature gradient. As the material cooled and layers were built, geometric contractions could occur due to thermal variations, resulting in residual stresses and potential deformations in the process.

The SLM printing process is an iterative one, requiring the division of geometry production into layers and stages. It involves two distinct stages: construction, where the sintering of layers corresponding to the cross-section of the geometry takes place, and cooling of the geometry after each iteration process.

2.2 Print parameters and material properties

The selected material for this research is the Ti-6Al-V4 alloy, a metallic composition composed of 6% aluminum and 4% vanadium in a titanium matrix. This alloy was chosen due to its physical, mechanical, and chemical properties, which

make it highly relevant and widely applied in the industry (Yang Guang and Xie, 2022). Recognized for its strength, lightness, and corrosion resistance, the Ti-6Al-V4 alloy is frequently employed in prominent sectors such as aerospace, automotive, and biomedical (AMFG, 2019). Its unique combination of characteristics makes it an ideal choice for applications that require high performance and durability.

A comprehensive study was conducted to determine the optimal power and speed values for fabricating the geometry using Ti-6Al-V4 material. Parametric single-bead simulation was employed to gather crucial insights into the melt pool characteristics during the AM process. This simulation provided valuable data on the melt pool's geometry, including width, length, and depth (Fig. 2).

By obtaining these preliminary data, it becomes possible to calibrate the machine settings according to the specific material being used. This calibration process allows for the identification of the most suitable configurations based on the observed behavior of the melt pool. With the objective of prioritizing faster printing speed, a value of 1000mm/s and a power of 250W were adopted in order to minimize voids between layers caused by inadequate material fusion.

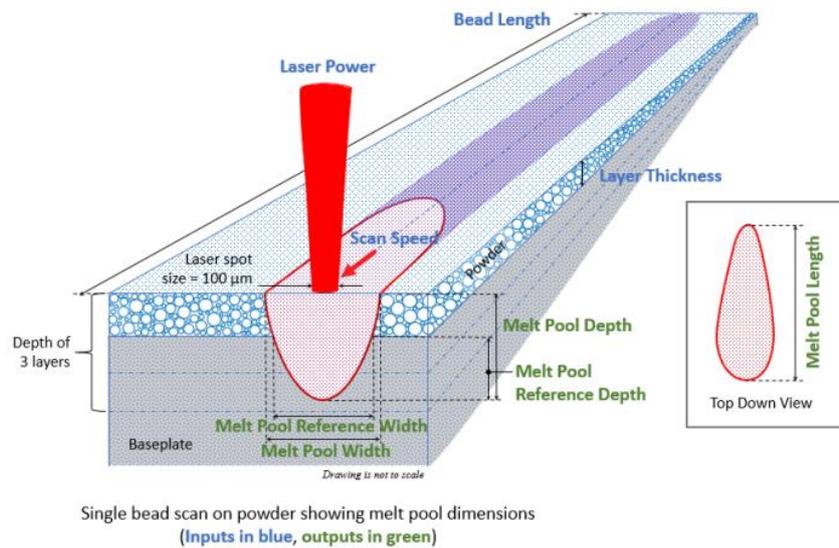


Figure 2. Melt pool parameters. Ansys. (2021).

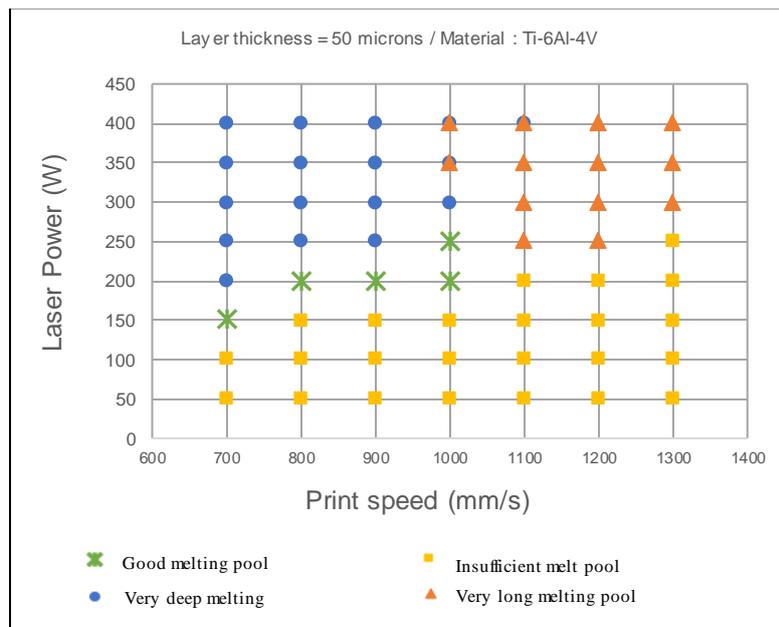


Figure 3. Melt pool simulation results.

In AM analysis, Ti-6Al-4V exhibits temperature-dependent properties (Tab. 1 and Fig. 4) and a fusion temperature of 1600°C, a crucial factor in determining the geometry's behavior during the manufacturing process, as the geometry

undergoes multiple heating and cooling cycles in its layers.

Table 1. Isotropic Elasticity properties of Ti-6Al-4V.

Temperature (C°)	Young's Modulus (GPa)	Poisson's Ratio	Coefficient of Thermal Expansion (C^-1)	Density (kg m^-3)
20	107	0,323	8,9E-06	4405
100	103,4	0,328	9,45E-06	4391,5
...
500	74,71	0,351	1,13E-05	4347
...
1000	16,29	0,38	1,16E-05	4274,3
...
1600	0,9435	0,415	-	4205,7

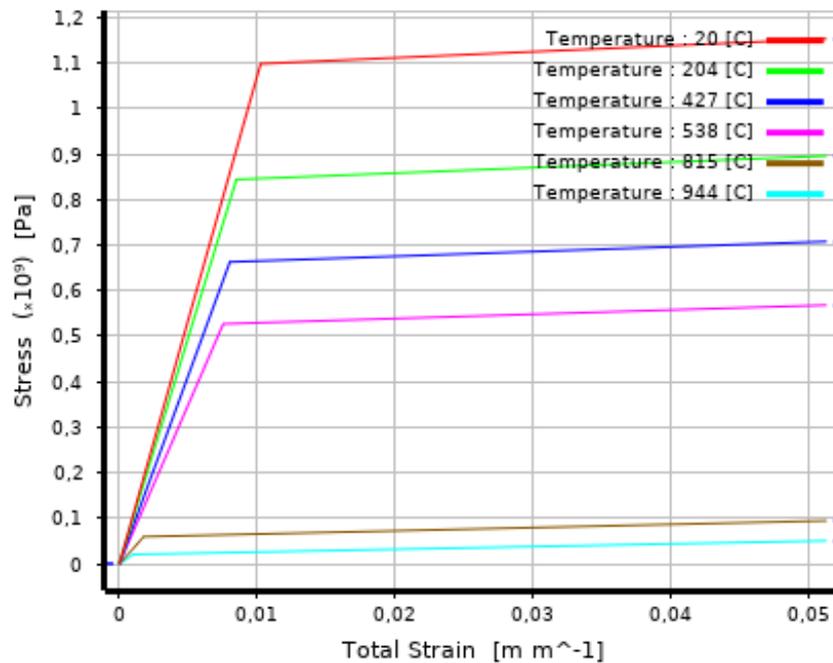


Figure 4. Bilinear Isotropic Hardening values.

2.3 Thermal and static analyses

Simulation of the manufacturing process requires the analysis to follow the actual build process, solidifying the part layer by layer. Since the thermal and structural aspects have a weak interaction, it is possible to initially simulate the thermal phenomena layer by layer and then use these temperature results in a subsequent structural simulation to determinate the contractions in model.

In an AM process simulation, the model evolves over time, meaning that elements are progressively added. Initially, the entire part is meshed with a layered mesh, and then the element birth and death technique are used to activate the element layers and simulate the build progression. Additionally, the relevant boundary conditions, such as thermal convection surfaces, also evolve.

The build process is considered complete when all the element layers have been added. The analysis times and time steps are determined by the process parameters and are not known in advance.

The model does not consider the beam scan pattern due to its complexity and computational cost. Actual metal powder deposit layers are aggregated into "super layers" of finite elements for simulation purposes. This grouping approach is appropriate since the temperature histories of adjacent layers are similar (Ansys. 2021).

For the AM process, the build platform is used as a reference for applying the preheating temperature gradient and convection, which varies depending on the type of material being used. This parameter is essential for minimizing

temperature variations during the printing process and also for improving adhesion of the print to the build platform in the initial layers. Figure 5 illustrates three stages in the printing process, showing the temperature variation during the layer processing.

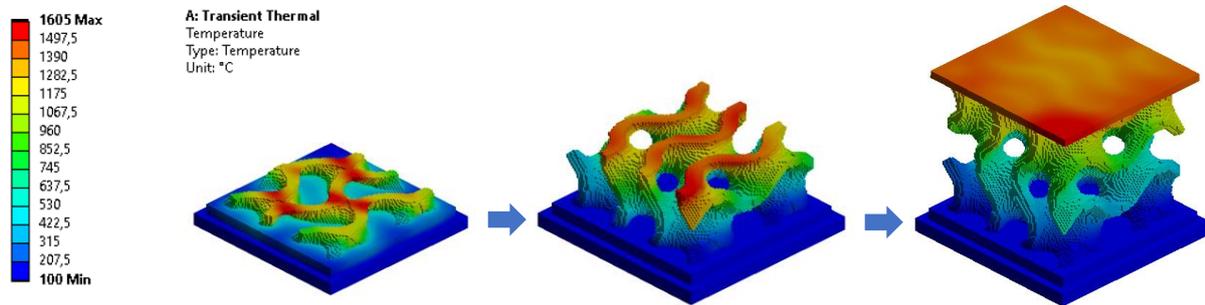


Figure 5. Evolution of print process.

In the structural analysis stage, the thermal loads from the AM process, coupled with compressive loading, are applied as boundary conditions (Fig. 6). Upon solving the static structural step, deformations, failures, and residual stress in the geometry can be evaluated in relation to the printing process. This evaluation process is conducted iteratively, examining the stress field history as a function of the layer printing time for the geometry. For the solution process, a nonlinear material with mechanical properties discussed in section 2.2 was considered. The plasticity model applied in the analysis was the isotropic bilinear model, with the addition of the "large deflection" function, which also enabled the evaluation of mesh contact or penetration during the solution.

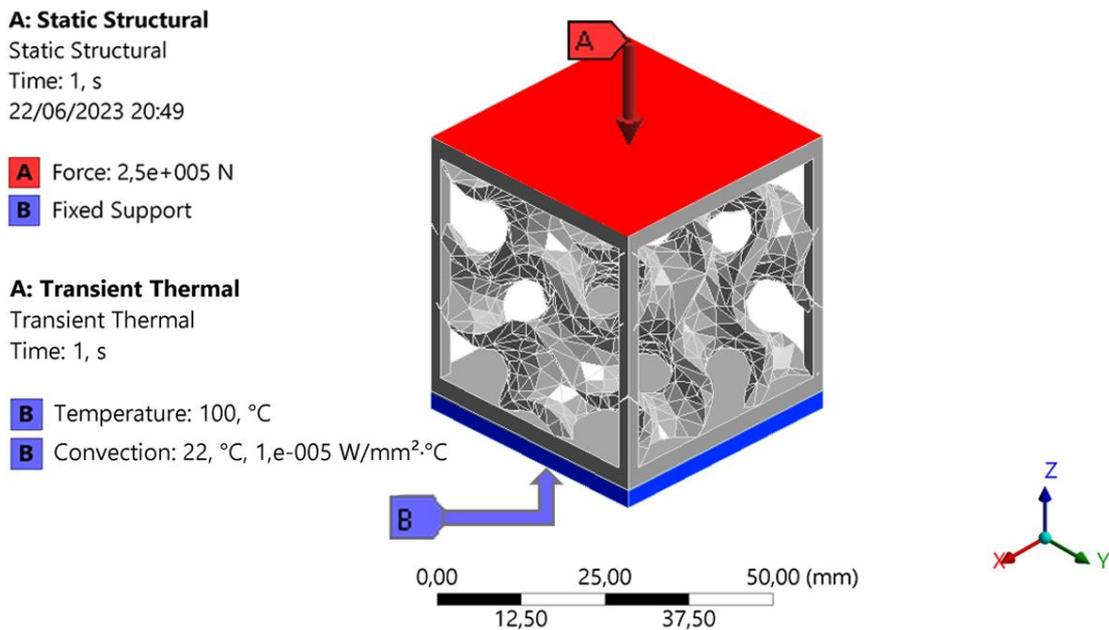


Figure 6. Boundary conditions for static and thermal analysis.

3. RESULTS AND DISCUSSIONS

Due to inherent processing flaws and inadequate cooling uniformity, dimensional distortions may arise in the fabricated geometry. These distortions primarily stem from variations in the contraction rate of the material at different temperatures, leading to permanent deformations in the geometry.

Deformations occurring during the AM process can significantly impact the geometrical precision and pose a risk to the successful completion of the process. The deposition of material onto the printing surface relies on a movable cylinder or blade, and any warping or distortion in the geometry can result in mechanical collisions with the intended part, thereby impeding the completion of the printing process (Yadroitsev et al., 2007).

Throughout the AM process, the metallic powder undergoes cyclic heating and cooling for each layer, as illustrated in Fig. 7. These thermal cycles are a recurring feature throughout the entire fabrication process.

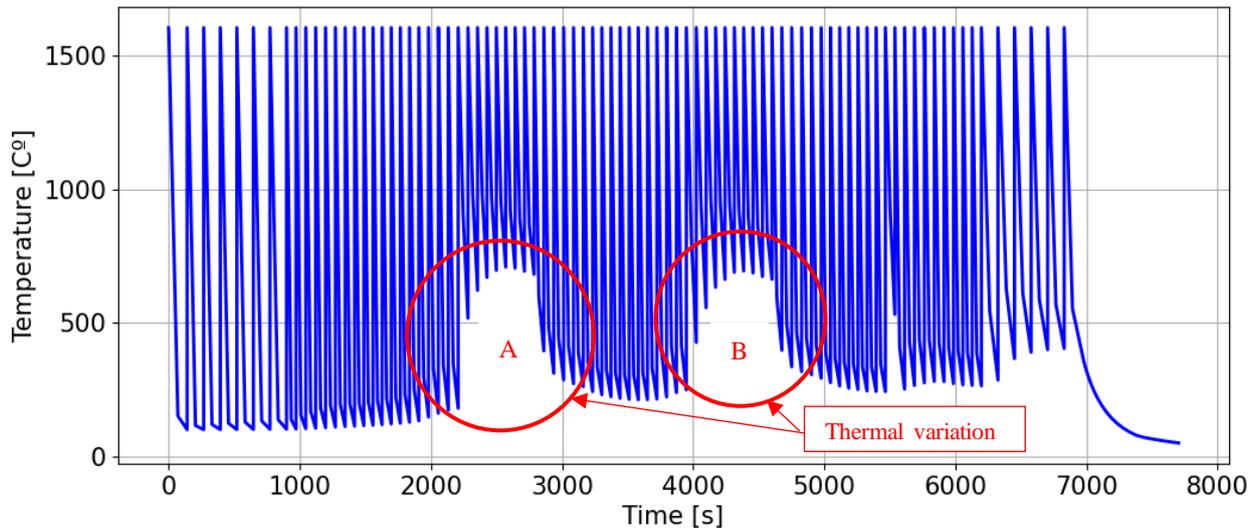


Figure 7. Thermal cycle of print process.

Using the graph to analyze the heating and cooling cycles, it is possible to observe areas with non-uniform cooling behavior compared to the other layers. This type of temperature variation occurs in fractions of the geometry that lack connections to supports or other parts of the object, resulting in areas with less material and compromising the cooling time between layers.

Based on the analysis of Figure 7, it was possible to determine the area affected by the variation in thermal cycles, as depicted in Fig. 8. These temperature variations result in residual stresses and dimensional distortions, as observed in Fig. 9. The absence of supports for the marked area led to permanent deformation in the geometry, compromising dimensional accuracy. This effect was observed in other areas of the component as well.

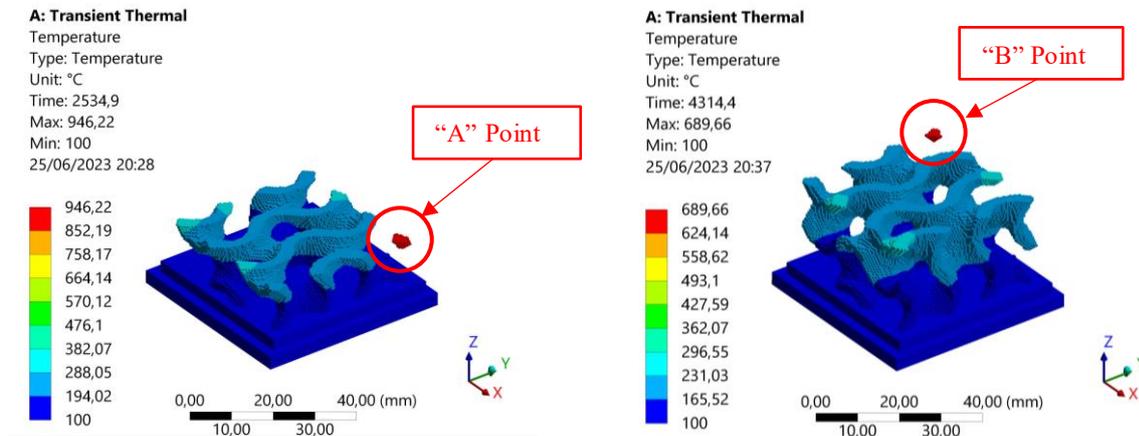


Figure 8. Thermal evaluation of heat source.

To address the discussed processing flaws, it was necessary to use complementary geometries known as supports. The purpose of these structures is to eliminate the deformation area highlighted in Fig. 8, minimizing excessive displacements of the geometry during the manufacturing process.

By comparing the two geometries shown in Fig. 9 and the graph in Fig. 10, a significant reduction in total deformation can be observed. As a result, there is an improvement in the convergence of numerical results due to the reduction of abrupt displacements.

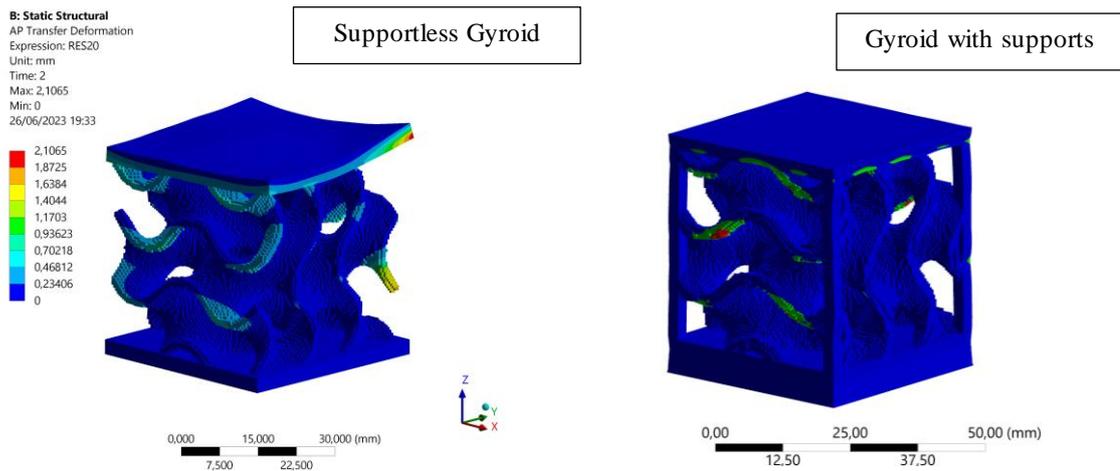


Figure 9. Implementation of support structures.

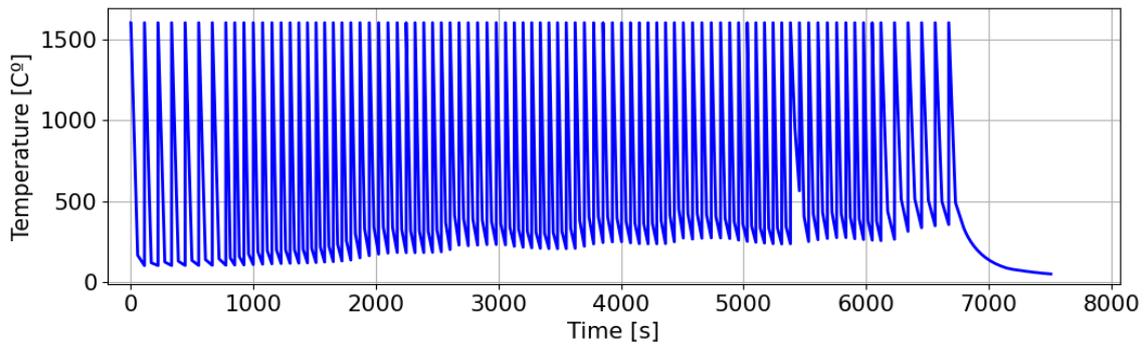


Figure 10. Improved temperature variation response in the processing cycle.

3.1 Compression analyses

The objective of the comparative simulation between the two geometries is to evaluate the influence of the SLM manufacturing process on the AM Gyroid in comparison of non-AM geometry (Base Gyroid). The simulation applies the boundary conditions as previous discussed, with a specific focus on the application of a 250kN load.

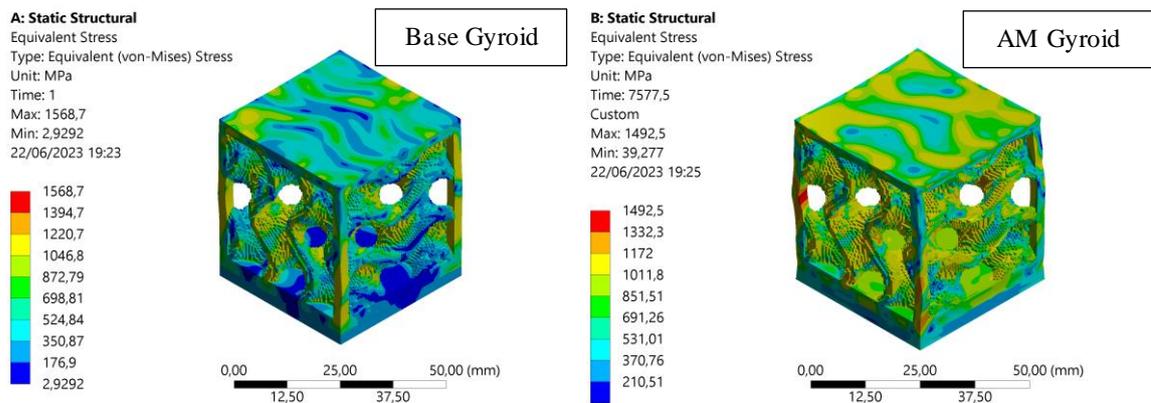


Figure 11. Equivalent (von-Mises) Stress comparative models.

Figure 11 depicts the von-Mises stress distribution across the entire specimen. The analysis reveals a pronounced variability in the stress field for the SLM-fabricated gyroid structure. This phenomenon can be ascribed to the thermal loading imparted during the laser-based manufacturing process. The successive cooling cycles induce plastic deformations due to material contraction, thereby engendering residual stresses throughout the geometry. Such residual

stresses significantly influence the structural performance under operational conditions.

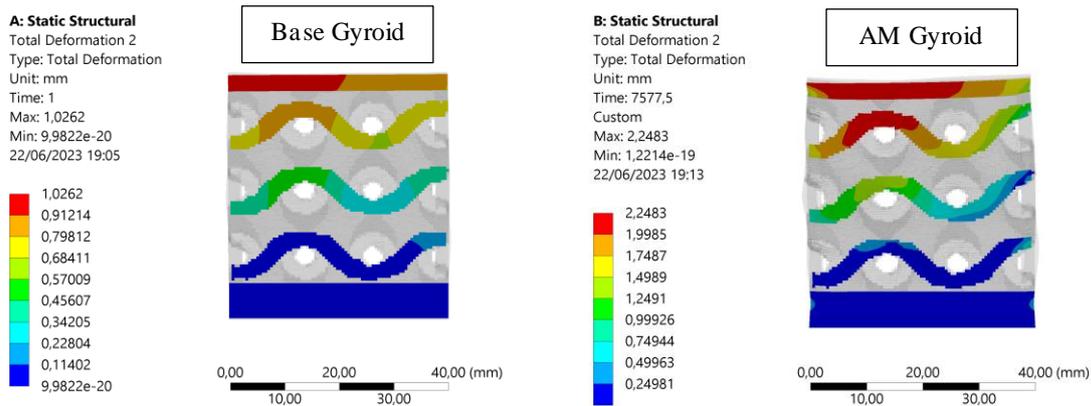


Figure 12. Total deformation comparative model.

As depicted in Figure 12, the geometry subjected to the AM process exhibited a deformation approximately twice as significant as a base geometry when subjected to the same magnitude of compressive loading.

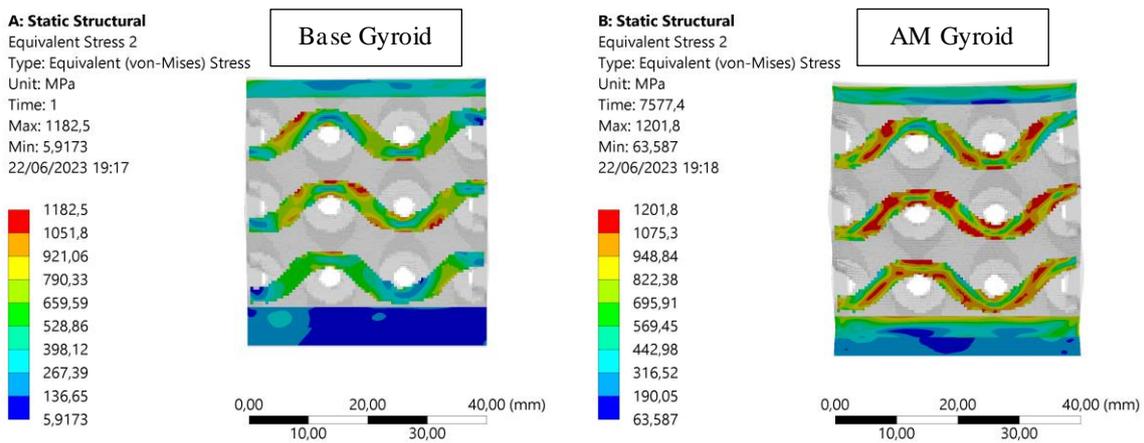


Figure 13. In plane Equivalent (von-Mises) stress comparative stress model.

Upon comparing the two geometries illustrated in Fig. 13, it becomes apparent that the geometry subjected to the AM process displays a significantly broader distribution of stress fields. This observation can be directly attributed to the occurrence of thermal cycles during the fabrication process, resulting in the generation of residual stresses within the geometry. Consequently, the affected regions are more susceptible to deformations and failures due to the presence of elevated stress levels. In order to further assess the performance of these two components, the maximum energy versus displacement relationship is evaluated and presented in Fig. 14.

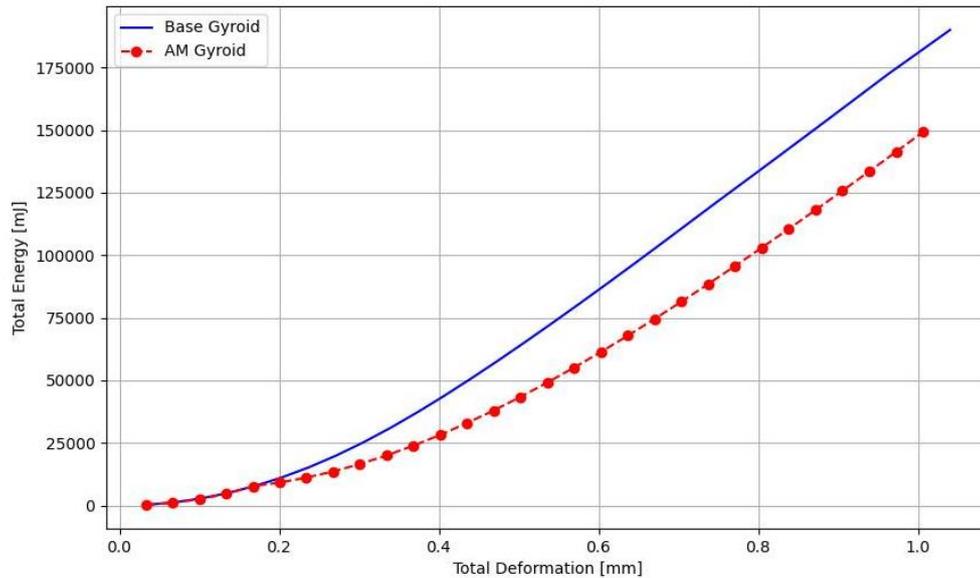


Figure 14. Comparative between base and AM Gyroid of maximum energy absorption.

4. CONCLUSIONS

The present study aimed to characterize the processing of gyroid-type geometries when subjected to the SLM manufacturing process. The complex nature of these geometries, combined with the absence of external walls in their modeling, led to observed dimensional instabilities during the simulations.

The investigation addressed several challenges, including geometry creation, processing considerations, and the application of appropriate boundary conditions for the AM process. The utilization of nonlinear materials and the SLM manufacturing process provided valuable insights and constituted a significant contribution to this research.

The exploration of printing parameters played a critical role in obtaining initial reference results for the processing of the selected material. Optimized power and speed settings were identified to enhance the strength and reliability of the AM process, minimizing failures and defects in the fabricated geometry.

Furthermore, the study focused on analyzing deformations resulting from the interaction between the laser and the material. This investigation provided valuable insights into dimensional distortions that can affect the performance and manufacturing of geometries using the AM process. Based on the collected data, support structures were strategically implemented at the model's edges to mitigate warping effects and improve the convergence of numerical results.

In conclusion, the proposed analysis methodology yielded satisfactory results by quantifying the impact of the AM process on the manufactured geometries. The study and analysis of the results enable the prediction of behavioral patterns and potential issues arising from the specific manufacturing method employed. These findings hold significant importance in the production of parts using the SLM process, considering the associated high manufacturing costs.

5. ACKNOWLEDGMENTS

The authors would like to thank CAPES (Coordination for the Improvement of Higher Education Personnel) and FAP-DF (Foundation for Research Support of the Federal District) for their financial support, as well as the Experimental and Computational Mechanics Group (GMEC) for their technical assistance in conducting this research.

6. REFERENCES

- Ansys. (2021). ANSYS engineering analysis system user's manual 2021.
- AMFG. (2019). A Guide to 3D Printing With Titanium.
- Ashby, M. F., & Gibson, L. J. (1997). Cellular Solids: Structure and Properties. 2nd ed. Cambridge University Press.
- Beaman, J. J., Bourell, D. L., Leub, M. C., & Rosenc, D. W. (n.d.). History of Additive Manufacturing and the 2009 Roadmap for Additive Manufacturing: Looking Back and Looking Ahead. *Procedia Manufacturing*.
- Hyde, S., Ninham, B. W., Andersson, S., Larsson, K., Landh, T., Blum, Z., & Lidin, S. (1997). *The Mathematics of Curvature. The Language of Shape*.
- Hyde, S. T., Kapfer, S. C., Mecke, K., Ams, C. H., & Schröder-Turk, G. E. (2011). Minimal surface scaffold designs for tissue engineering. *Biomaterials*.
- Khaderi, S. N., Deshpande, V. S., & Fleck, N. A. (2014). The stiffness and strength of the gyroid lattice. *International*

Journal of Solids and Structures.

- Mecke, K., Schröder-Turk, G. E., Winter, B., Butz, B., Dieker, C., & Spiecker, E. (2015). Coexistence of both gyroid chiralities in individual butterfly wing scales of *Callophrys rubi*. *Proceedings of the National Academy of Sciences*.
- Milewski, J. O. (2017). Additive Manufacturing of Metals: From Fundamental Technology to Rocket Nozzles, Medical Implants, and Custom Jewelry. *Additive Manufacturing of Metals*.
- Schoen, A. H. (1970). Infinite periodic minimal surfaces without self-intersections.
- Smurov, I., Bertrand, P., Ludovic, T., & Yadroitsev, I. (2007). Strategy of manufacturing components with designed internal structure by selective laser melting of metallic powder. *Applied Surface Science*, 254, 980–983.
- Xiao, B., & Zhang, Y. (2007). Laser sintering of metal powders on top of sintered layers under multiple-line laser scanning. *Journal of Physics D: Applied Physics*.
- Yang Guang, Z. S. Xie, R. Y. Y., & W. C. (2022). Methods and Mechanism of Powder Mixing for Selective Laser Melting. *Manufacturing Technology Journal*.

7. RESPONSIBILITY NOTICE

The authors are responsible for the printed material included in this paper.